

Contract: Gammadot Rheology  
Compound Ref: Std. Black Natural




Batch / Sample No: 888 / 01  
Generic Type: NR

Test Date: 25<sup>th</sup> October 2007  
Operator: MCE

Run No.	M <sub>H</sub>	M <sub>L</sub>	t <sub>s2</sub>	t' <sub>c</sub> (5)	t' <sub>c</sub> (25)	t' <sub>c</sub> (50)	t' <sub>c</sub> (90)
01	69.82	8.25	2:25	2:49	4:12	4:44	6:30
02	69.78	7.72	2:20	2:48	4:08	4:40	6:24
03	69.48	7.57	2:20	2:46	4:07	4:39	6:25

MH=Max. Torque(lb-in), ML=Min. torque(lb-in), ts2=Scorch Time (min:sec), t'<sub>c</sub>(n)=% Cure Time (min:sec)

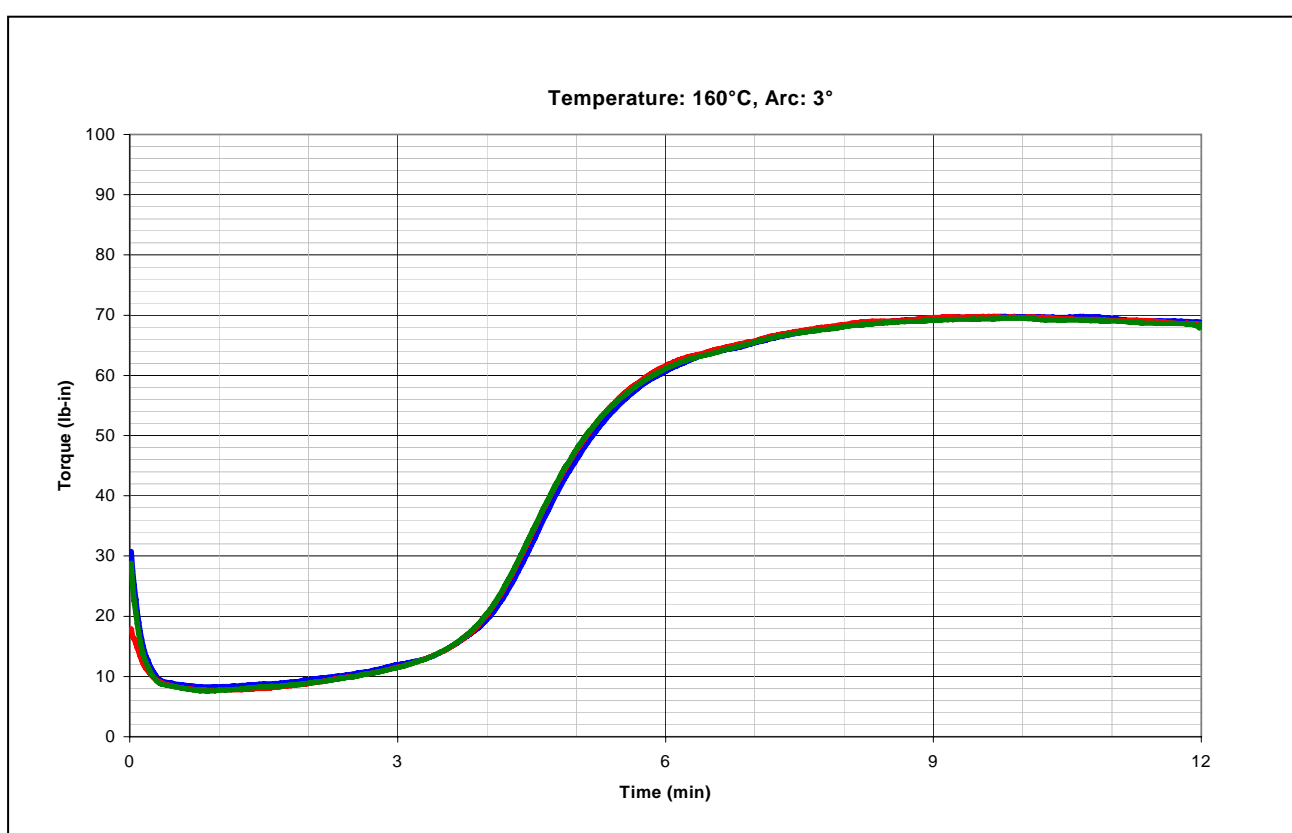

**Notes:**

No anomalous behaviour was observed during testing.